

EN 29053 - Determination of airflow resistance

Direct airflow method - method A

Client: Kvadrat


Date: 24-02-20

Type: Mozaic 2
Colour: 262 & 472
Order:
Batch:
Manufacturer: Febrik

27% new wool
9% nylon
12% polyester
6% elasthan
46% polyester filling

Specimen Diameter: 100 mm
Thickness: 3.3 mm
Area specific mass: 805 g/m²

u_l (mm/s)	$R_{s,l}$ (Pa s/m)
16.53	407
14.16	409
11.80	409
9.44	410
7.12	407
4.80	397

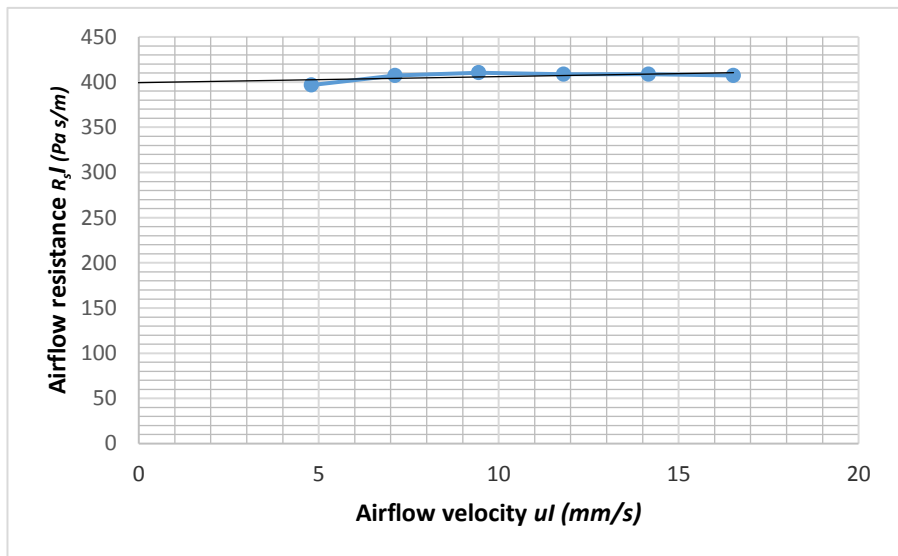

Airflow Resistance

$R_s = 399$ Pa s/m