# **Test Report**

Report Number: 236841-1-PMI



**INSTITUTE** 

Gregersensvej 1 DK-2630 Taastrup +45 72 20 20 00 info@teknologisk.dk www.teknologisk.dk

Page 1 of 4 Init.: CHF/LELN Order no.: 236841 Encl.: 2

Assignor: KVADRAT A/S, Lundbergsvej 10, DK-8400 Ebeltoft

Item: Sample of upholstered material designated: Balboa, 003

Detailed information is given in enclosure A.

Sampling: The assignor confirms having selected the product. The product was forwarded by the

assignor and received at Danish Technological Institute on 25 January 2024.

**Period:** The test took place from 26 January 2024 to 30 January 2024.

Method: BS 5852:2006 Methods of test for assessment of the ignitabability of upholstered seating by

smoldering and flaming ignitions sources. Sources 1,2 and 3 (flame) and sources 4,5,6 og 7

(wooden crib)

**Test results:** According to the criteria of ignition described in BS 5852:2006, source 5, clause 4, the result

is:

Non-ignition > PASSES

The results are shown in enclosure A.

**Terms:** This test was conducted accredited in accordance with international requirements (ISO/IEC

17025:2017) and in accordance with the General Terms and Conditions of Danish

Technological Institute. The test results solely apply to the tested item. This test report may be quoted in extract only if Danish Technological Institute has granted its written consent.

Place: Danish Technological Institute, Taastrup, Environmental Technology

Signature: This document is only valid with a digital signature from Danish Technological Institute. The

date of issue appears from the digital signature.

Charlotte Fischer Senior Consultant





### **Materials**

Item: Sample of upholstered material designated: Balboa, 003

Combination of upholstered material tested:

Cover:

Designated: Balboa, 003

Composition: 100% polyester FR Approximate mass per area: 681 g/m<sup>2</sup>

Filling: Flame-retardant CMHR foam designated: CMHR 3538/RG35150.

Approximate density: 35 kg/m<sup>3</sup>

(Foam was provided by the test laboratory.)

#### Results

Test method: BS 5852:2006

Ignition source: Crib 5. Weight 17±1 g.

Water soaking: Before testing the sample was not subjected to the water soaking and drying

procedure described in BS 5852:2006, Annex E.

Conditioning atmosphere: 23±2 °C / 50±5 % RH

Test result: Non-ignition > PASSES

	Test 1	Test 2
Duration of flames [min:sec]	05:50	05:54
Smouldering ceased within 60 minutes	Yes	Yes
Damage in the horizontal (seat) component:		
Length [mm]	23	30
Width [mm]	38	37
Thickness [mm]	68	57
Damage in the vertical (back) component:		
Width [mm]	28	25
Thickness [mm]	62	37

The above test results relate only to the ignitability of the combination of materials under the particular conditions of test; they are not intended as a means of assessing the full potential fire hazard of the materials in use.



#### Criteria for failure

According to BS 5852:2006 Clause 4.1.1 all of the following behaviours shall be deemed to be progressive smouldering ignition (regarding crib 5):

- a. Escalating combustion behaviour so that it is unsafe to continue the test and requires forcible extinction.
- c. Smouldering until the specimen is essentially consumed or to the extremities of the specimen that is either the sides or to its full thickness, within the test duration (60 minutes).
- e. Production of externally detectable amounts of smoke, heat or glowing 60 minutes after ignition of the crib.
- f. On final examination: Evidence of charring other than discolouration, more than 100 mm in any direction, apart from upwards, from the nearest part of the original position of the source.


According to Clause 4.2.1 all of the following behaviours shall be deemed to be flaming ignition (regarding crib 5):

- a. Escalating flaming combustion behaviour so that it is unsafe to continue the test and forcible extinction if required.
- b. Burning until the specimen is essentially consumed within the test duration.
- c. Flame front reaches either the sides or passes through the full thickness of the specimen within the duration of the test.
- e. Flaming for more than 10 minutes after ignition of the crib.
- g. Flaming debris causing an isolated floor fire that continues to flame longer than 10 minutes.



## **Photos**

Test of: Sample of upholstered material designated: Balboa, 003

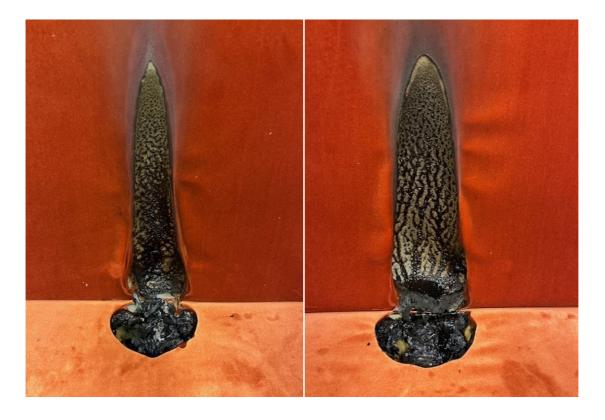

236841-1-PMI Enclosure B, Page 4 of 4