

AWTA PRODUCT TESTING

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing
A.B.N 43 006 014 106


1st Floor, 191 Racecourse Road, Flemington, Victoria 3031
P.O Box 240, North Melbourne, Victoria 3051
Phone (03) 9371 2400

TEST REPORT

Client : Kvadrat A/S
Lundbergsvej 10
Ebeltoft 8400
Denmark

Test Number : 25-004542
Issue Date : 26/11/2025
Print Date : 26/11/2025

Sample Description Clients Ref : "Asator"
Velour woven fabric
Colour : Grey
End Use : Upholstery
Nominal Composition : 100% Cotton
Nominal Mass per Unit Area/Density : 530g/lin.m

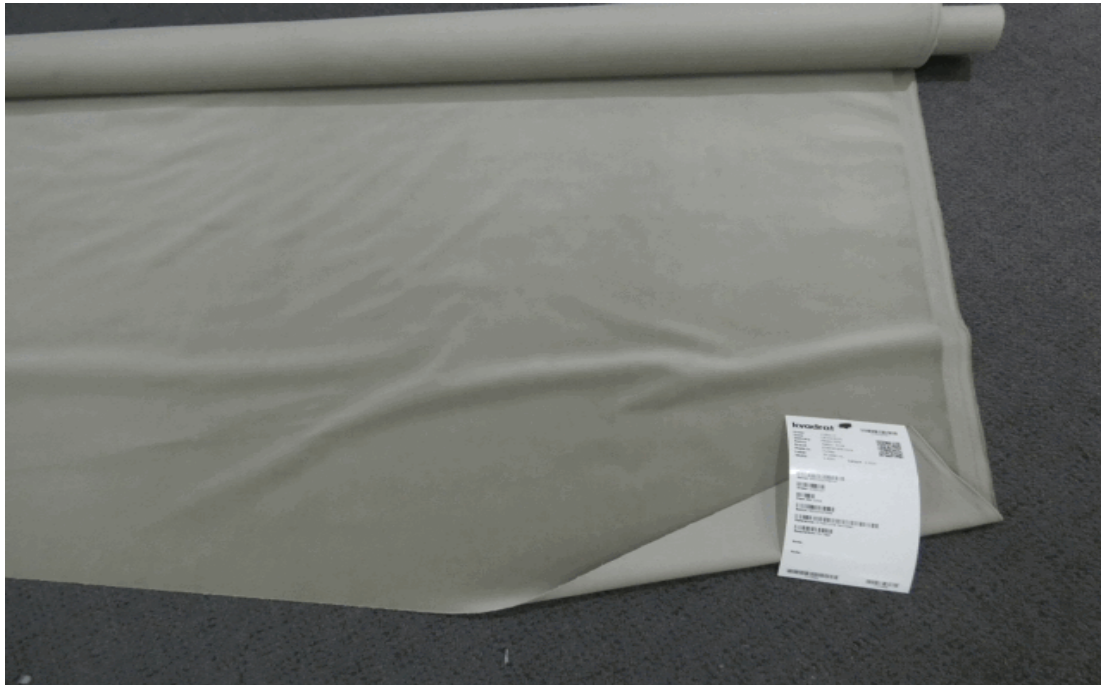

365286

80273

Page 1 of 2

© Australian Wool Testing Authority Ltd
Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing
Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

Fiona McDonald

APPROVED SIGNATORY



MICHAEL A. JACKSON B.Sc.(Hons)
MANAGING DIRECTOR

AWTA PRODUCT TESTING

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing
A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031
P.O Box 240, North Melbourne, Victoria 3051
Phone (03) 9371 2400

TEST REPORT

Client : Kvadrat A/S
Lundbergsvej 10
Ebeltoft 8400
Denmark

Test Number : 25-004542
Issue Date : 26/11/2025
Print Date : 26/11/2025

AS 1530.2-1993

**Methods for Fire Tests on Building Materials, Components and Structures.
Part 2: Test for Flammability of Materials**

Date Tested	25-11-2025	
Flammability Index	73	
	Length	Width
Spread Factor	40	40
Speed Factor	49	48
Heat Factor	19	25
Maximum height (d)		
Mean	21.0	21.0
Coefficient of Variation	0.0	0.0 %
Time		
Mean	30.5	30.9
Coefficient of Variation	4.3	3.8 %
Heat (a)		
Mean	78.0	104.7
Coefficient of Variation	19.6	25.9 %
Number of Specimens Tested	6	9
Observation	Visible smoke, Burning	

Tested as received.

These test results relate only to the behaviour of the test specimens of the material under the particular conditions of the test, and they are not intended to be the sole criterion for assessing the potential fire hazard of the material in use.

365286

80273

Page 2 of 2

© Australian Wool Testing Authority Ltd
Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing
Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



Fiona McDonald

APPROVED SIGNATORY

MICHAEL A. JACKSON B.Sc.(Hons)
MANAGING DIRECTOR