

**Curtain Fabric Type Outer View by Kvadrat A/S**

**Determination of airflow resistance according to  
DIN EN ISO 9053-1**

Report No. B300031-01/TB03 Index A  
22 October 2025

Client:  
Kvadrat A/S  
Lundbergsvej 10  
8400 Ebeltøft

Müller-BBM Building Solutions GmbH  
www.mbbm-bso.com

Branch office Planegg  
Helmut-A.-Müller-Straße 1 - 5  
82152 Planegg

Philipp Meistring  
☎ +49 89 3540486 38  
philipp.meistring@mbbm-bso.com

**Table of contents**

<b>1</b>	<b>Task .....</b>	<b>2</b>
<b>2</b>	<b>Basis.....</b>	<b>2</b>
<b>3</b>	<b>Test object.....</b>	<b>2</b>
<b>4</b>	<b>Execution of measurements .....</b>	<b>2</b>
<b>5</b>	<b>Measurement results.....</b>	<b>3</b>
<b>6</b>	<b>Remarks .....</b>	<b>3</b>
	<b>Appendix A – Test certificates.....</b>	<b>4</b>
	<b>Appendix B – Description of the test procedure for the determination of the airflow resistance.....</b>	<b>8</b>

## 1 Task

On behalf of Kvadrat A/S, 8400 Ebeltoft, Denmark, the airflow resistance of the fabric type Outer View was to be determined according to DIN EN ISO 9053-1 [1].

## 2 Basis

This test report is based on the following document:

- [1] DIN EN ISO 9053-1: Acoustics – Determination of airflow resistance – Part 1: Static airflow method (ISO 9053-1:2018); German version EN ISO 9053-1:2018. March 2019
- [2] DIN EN ISO 5084: Textiles – Determination of thickness of textiles and textile products (ISO 5084:1996); German version EN ISO 5084:1996. 1996-10

## 3 Test object

The tested fabric is described in Table 1. The samples were taken by the testing laboratory from a fabric roll delivered by the client. Each sample had dimensions of 210 mm x 297 mm. The following characteristics were determined by the testing laboratory:

Table 1. Test object.

Test object (information provided by the client / indication on samples)	Sample No.	Area specific mass <i>m'</i> [g/m <sup>2</sup> ]	Thickness <i>t</i> [mm]
Fabric type Outer View, composition: 70 % REC PES FR, 30 % PES	1	208	0.62
	2	209	0.63
	3	207	0.62
Mean		208	0.62

The thickness of the fabric was determined acc. DIN EN ISO 5084 [2] (per sample mean value of three positions, pressure 1.00 kPa, pressure-foot 2000 mm<sup>2</sup>).

## 4 Execution of measurements

The airflow resistance was determined according to DIN EN ISO 9053-1 [1].

The test method, the test facility and the test equipment used are described in Appendix B.

## 5 Measurement results

The measurement results are shown in the diagram and table in the test certificates in Appendix A of this report.


For the tested fabric the following specific airflow resistance was determined:

Table 2. Specific airflow resistance.

Test object Fabric type Outer View	Specific airflow resistance $R_s$ / (Pa s / m)	Appendix A, page
Sample 1	24	1
Sample 2	23	2
Sample 3	25	3
Mean	24	--

## 6 Remarks

The test results exclusively relate to the investigated subjects and conditions described.



M.Eng. Philipp Meistring  
(Project manager)

This test report may only be published, shown or copied as a whole, including its appendices. The publishing of excerpts is only possible with prior consent of Müller-BBM.



Testing laboratory accredited by DAkkS according to  
DIN EN ISO/EC 17025:2018.  
The accreditation is valid only for scope listed in the annex  
of the accreditation certificate.

**Appendix A – Test certificates**

EN ISO 9053-1  
Determination of airflow resistance

**Client:** Kvadrat A/S  
Lundbergsvej 10  
8400 Ebeltøft

**Project number:** B300031-01

**Sample number:** 15909-1


**Test object:** - fabric: Outer View  
- material: 70 % REC PES FR, 30 % PES

sample 1

Diameter: 100 mm  
Thickness: 0.62 mm  
Area-specific mass: 208 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96.6$  kPa  
Temperature:  
 $\theta = 23.3$  °C  
Relative humidity:  
 $r. h. = 25.3$  %

$u/$ (mm/s)	$R_s/$ (Pa s/m)
4.69	24
6.09	24
7.49	23
8.89	23
10.28	23
11.68	23
13.09	23

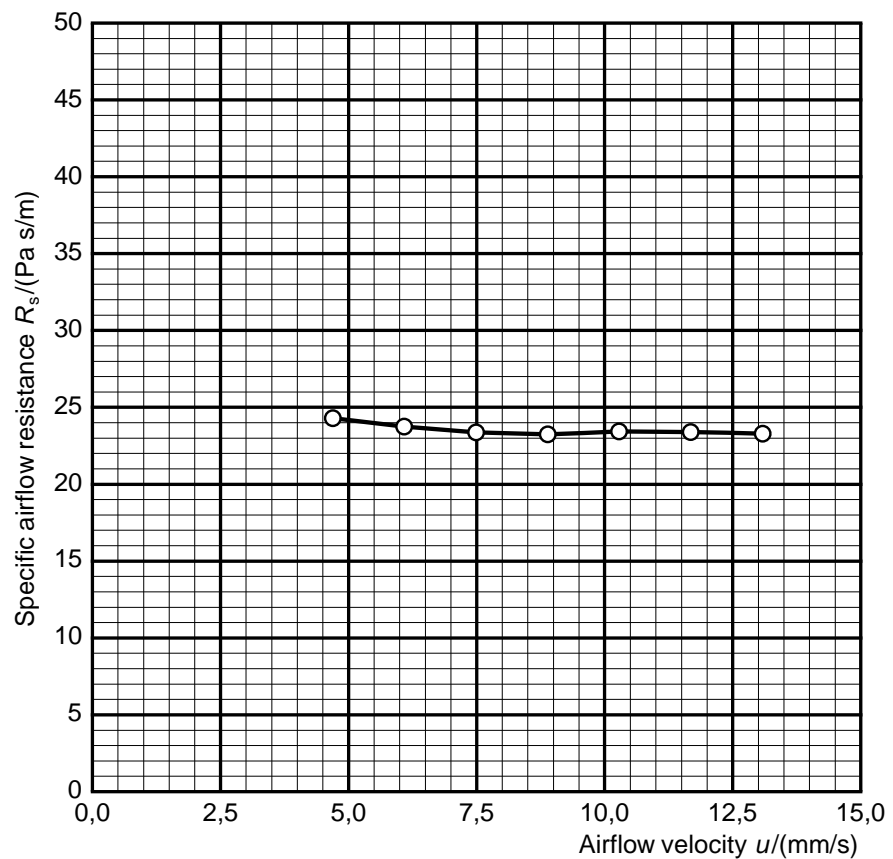

Specific airflow resistance  $R_s(0.5 \text{ mm/s}) = 24 \text{ Pa s/m}$

Laboratory: Planegg  
Responsible: Moll  
Date: 2025-10-10

EN ISO 9053-1  
Determination of airflow resistance

**Client:** Kvadrat A/S  
Lundbergsvej 10  
8400 Ebeltøft

**Project number:** B300031-01

**Sample number:** 15909-2


**Test object:** - fabric: Outer View  
- material: 70 % REC PES FR, 30 % PES

sample 2

Diameter: 100 mm  
Thickness: 0.63 mm  
Area-specific mass: 209 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96.6$  kPa  
Temperature:  
 $\theta = 23.4$  °C  
Relative humidity:  
 $r. h. = 18.1$  %

$u/$ (mm/s)	$R_s/$ (Pa s/m)
4.69	24
6.09	23
7.49	23
8.89	23
10.28	23
11.68	23
13.08	23

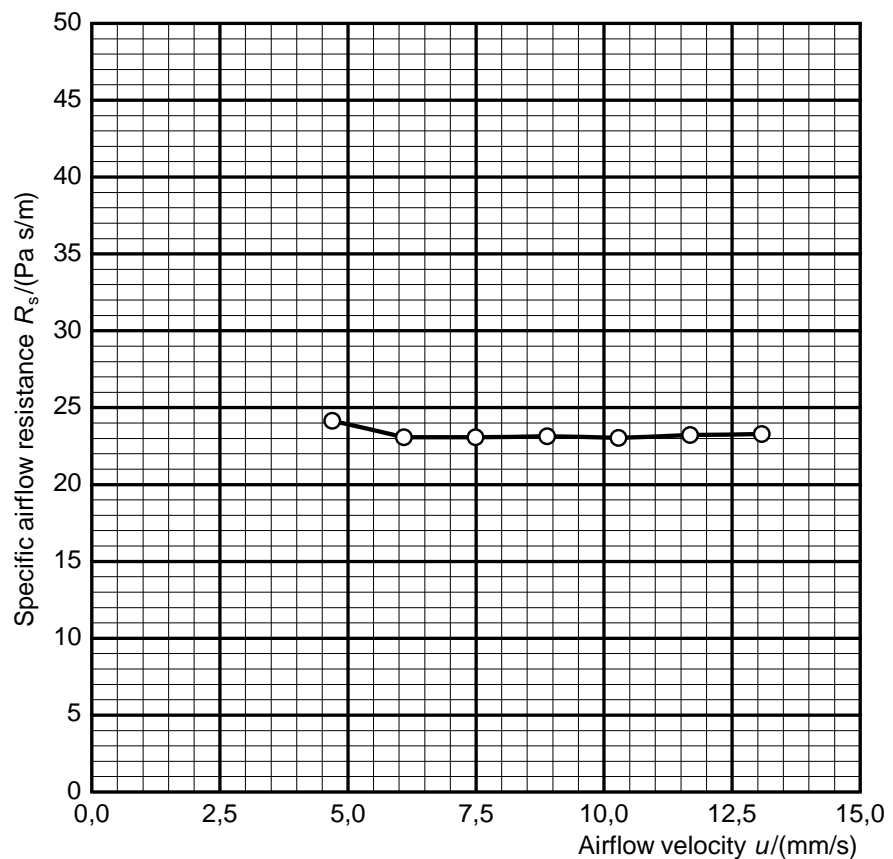

Specific airflow resistance  $R_s(0.5 \text{ mm/s}) = 23 \text{ Pa s/m}$

Laboratory: Planegg  
Responsible: Moll  
Date: 2025-10-10

EN ISO 9053-1  
Determination of airflow resistance

**Client:** Kvadrat A/S  
Lundbergsvej 10  
8400 Ebeltøft

**Project number:** B300031-01

**Sample number:** 15909-3

**Test object:** - fabric: Outer View  
- material: 70 % REC PES FR, 30 % PES

sample 3


Diameter: 100 mm  
Thickness: 0.62 mm  
Area-specific mass: 207 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96.6$  kPa

Temperature:  
 $\theta = 23.5$  °C

Relative humidity:  
 $r. h. = 14.4$  %

$u/$ (mm/s)	$R_s/$ (Pa s/m)
4.69	26
6.09	25
7.49	25
8.89	25
10.29	25
11.68	25
13.08	25

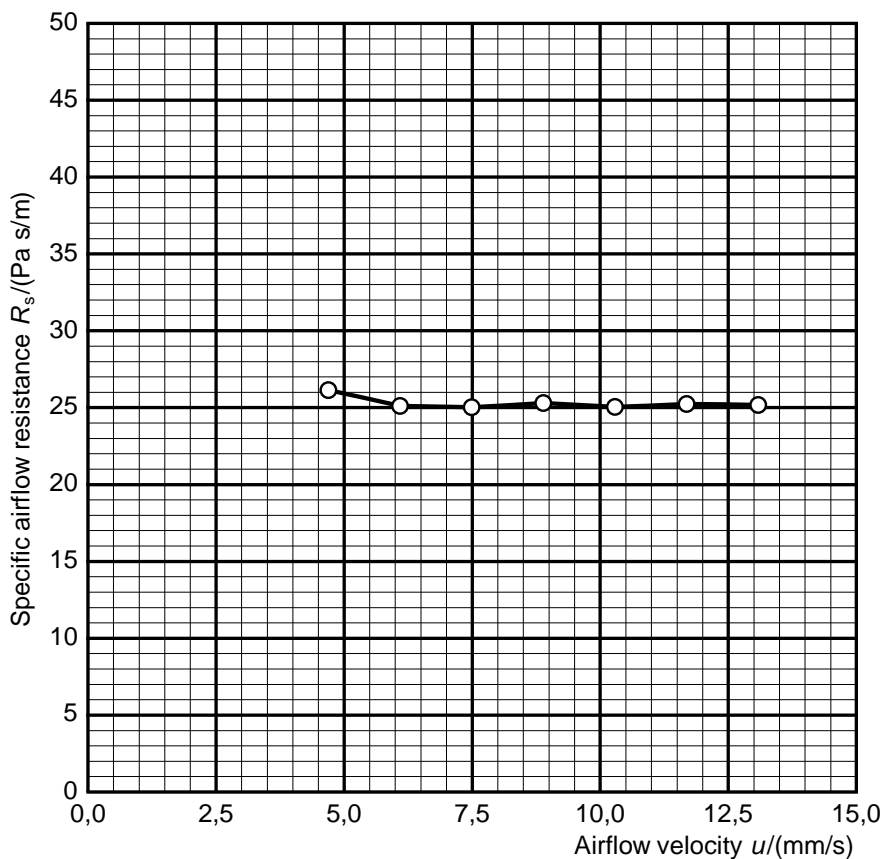

Specific airflow resistance  $R_s(0.5 \text{ mm/s}) = 25 \text{ Pa s/m}$

Laboratory: Planegg  
Responsible: Moll  
Date: 2025-10-10

## Appendix B – Description of the test procedure for the determination of the airflow resistance

### B.1 Measurand

The specific airflow resistance  $R_S$  of the test object was determined. For this purpose the air pressure difference in front of as well as behind the test object was measured at different volumetric airflow rates. The specific airflow resistance  $R_{S,i}$  for each volumetric airflow rate  $q_{v,i}$  determined was calculated using the following equation:

$$R_{S,i} = \frac{\Delta p_i \cdot A}{q_{v,i}}$$

With

$R_{S,i}$  specific airflow resistance in Pa s/m;

$\Delta p_i$  air pressure difference across the test object with respected to the atmosphere in Pa;

$A$  cross-sectional area of the test object perpendicular to the direction of flow in m<sup>2</sup>;

$q_{v,i}$  volumetric airflow rate passing through the test object in m<sup>3</sup>/s;

$u_i$  linear airflow velocity in m/s;

In addition the linear airflow velocity  $u_i$  was determined:

$$u_i = \frac{q_{v,i}}{A}$$

The indicated measurement result is the specific airflow resistance  $R_S$ , which is calculated for an airflow velocity of  $u = 0.0005$  m/s by extrapolation with help of the linear regression.

### B.2 Test procedure

The direct airflow method (static airflow method according to DIN EN ISO 9053-1 [1]) was applied. A steady unidirectional airflow with different air flow rates is pressed through the test object in the specimen holder. The resulting pressure drop between the two free faces of the test object is measured.

The specimen holder had a diameter of  $D = 100$  mm.

### B.3 List of test equipment

The test equipment used is listed in Table B.1.

Table B.1. Test equipment.

<b>Name</b>	<b>Manufacturer</b>	<b>Type</b>	<b>Serial-No.</b>
Measurement system airflow resistance	Müller-BBM	M89319-00	315003
Software for measurement and evaluation	Müller-BBM	m ars	Version 1.23.8256. 29682
Thickness gauge	Hans Schmidt & Co GmbH	D-2000-C0913	2985
Electronic balance	Kern	KB1200-2N	W1402353