

# EN 29053 - Determination of airflow resistance

Direct airflow method - method A


Client Sahco / Kvadrat

Date: 27-07-20

Fabric details Type: Space 100% Polyester FR  
Colour: 2  
Order:  
Pick:  
Manufacturer: Sahco

Specimen Diameter: 100 mm  
Thickness: 0.57 mm  
Area specific mass: 294 g/m<sup>2</sup>

$u_l$ (mm/s)	$R_{s,l}$ (Pa s/m)
16.53	2528
14.16	2518
11.80	2503
9.44	2490
7.12	2455
4.80	2393

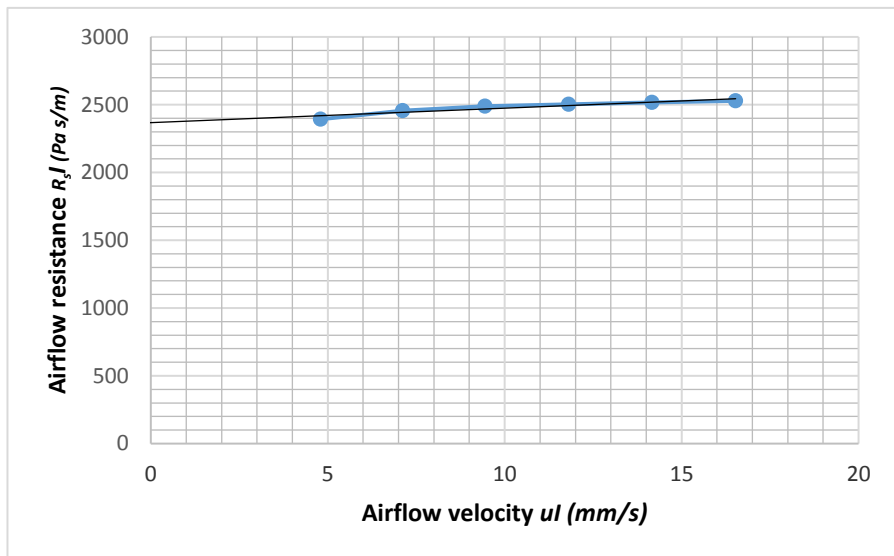

**Airflow Resistance**

**$R_s = 2373$  Pa s/m**