

# Sound Absorption Coefficient ISO 354

Measurement of absorption in reverberation rooms

**Client** Kinnasand

**Test Specimen** Curtains

Folded 100%

**Wall mounting with 100mm distance**

One layer of textile

Textile: Twinx

from Kinnasand  
100% polyester FR

colour:

26

**Test Build-Up (from top to bottom):**

1 mm	Front textile
100 mm	Air gap
	Reflective wall

**Mounting**

100mm distance to the wall

1 layer of curtains, 2 elements 4000x3000mm with approx.

20mm overlap, 100% folded, 200% textile length

Total dimensions of the test object

L x H = 3980mm x 3000mm




Room: Reverberation Room

Volume: 156 m<sup>3</sup>

Size: 11.94 m<sup>2</sup>

Date of test 25-10-19

Frequency [Hz]	as 1/3 octave	ap octave
100	0.04	
125	0.06	0.05
160	0.06	
200	0.08	
250	0.08	0.10
315	0.08	
400	0.10	
500	0.10	0.10
630	0.11	
800	0.10	
1000	0.11	0.10
1260	0.11	
1600	0.12	
2000	0.13	0.15
2500	0.14	
3160	0.16	
4000	0.17	0.20
5000	0.19	

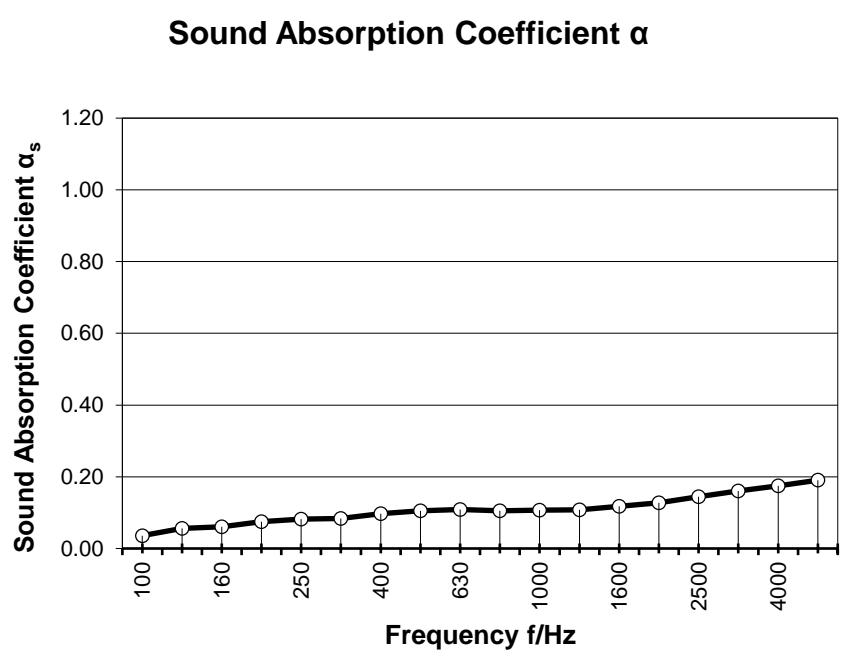

as Sound absorption coefficient to ISO 354

ap Practical sound absorption coefficient to ISO 11654

Rating according to ISO 11654:

NRC:	0.10
SAA:	0.1

**Weighted Sound Absorption Coefficient  $\alpha_w = 0.15$**

Sound absorption class:E

**kvadrat soft cells**

Test conducted by Kvadrat SoftCells  
Poznańska 3, 62-023 Gądki