

Sound Absorption Coefficient ISO 354

Measurement of absorption in reverberation rooms

Client Kinnasand

Test Specimen Curtains
Flat

Wall mounting - 100mm distance

One layer of textile

Textile: Fields from Kinnasand colour: 25
100% Trevira CS

Test Build-Up (from top to bottom):

1 mm	Front textile
100 mm	Air gap
	Reflective wall

Mounting

100mm distance to the wall

Flat curtains 1 element 4000x3000mm

Total dimensions of the test object

L x H = 4000mm x 3000mm

Room: Reverberation Room

Volume: 156 m³

Size: 12.00 m²

Date of test 25-10-19




Frequency [Hz]	α_s 1/3 octave	α_p octave
100	0.00	
125	0.00	0.00
160	0.01	
200	0.02	
250	0.03	0.05
315	0.04	
400	0.06	
500	0.08	0.10
630	0.11	
800	0.12	
1000	0.13	0.10
1260	0.10	
1600	0.08	
2000	0.10	0.10
2500	0.12	
3160	0.11	
4000	0.12	0.10
5000	0.12	

α_s Sound absorption coefficient to ISO 354

α_p Practical sound absorption coefficient to ISO 11654

Rating according to ISO 11654:

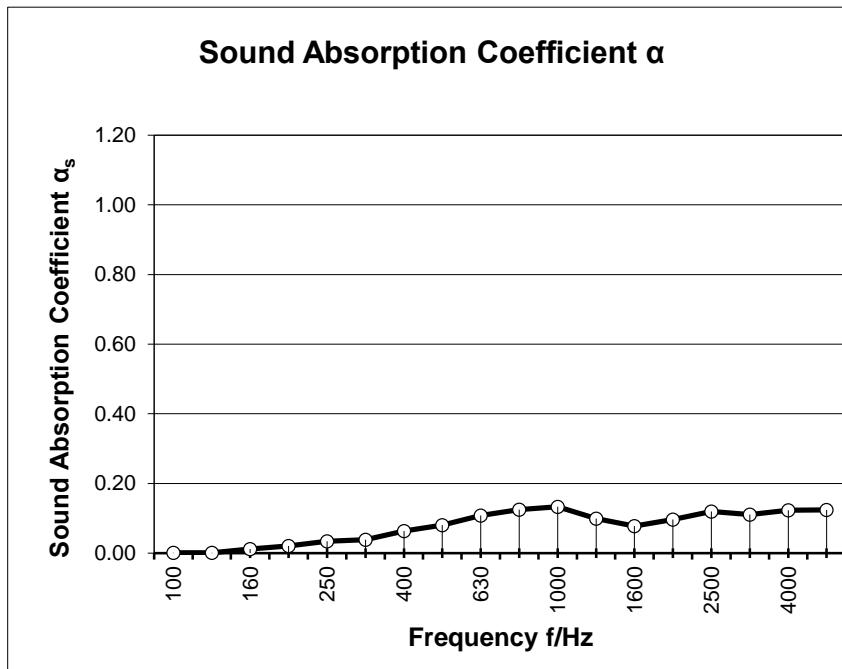

NRC:	0.10
SAA:	0.08

Weighted Sound Absorption Coefficient $\alpha_w = 0.1$

Sound absorption class:-

Sound Absorption Coefficient ISO 354

Measurement of absorption in reverberation rooms

Client Kinnasand

Test Specimen Curtains

Folded 100%

Wall mounting with 100mm distance

One layer of textile

Textile: Fields from Kinnasand
100% Trevira CS colour: 25

Test Build-Up (from top to bottom):

1 mm	Front textile
100 mm	Air gap
	Reflective wall

Mounting

100mm distance to the wall

1 layer of curtains, 2 elements 4000x3000mm with approx.

20mm overlap, 100% folded, 200% textile length

Total dimensions of the test object

L x H = 3980mm x 3000mm




Room: Reverberation Room

Volume: 156 m³

Size: 11.94 m²

Date of test 25-10-19

Frequency [Hz]	as 1/3 octave	ap octave
100	0.03	
125	0.05	0.05
160	0.09	
200	0.11	
250	0.13	0.15
315	0.14	
400	0.16	
500	0.17	0.15
630	0.17	
800	0.16	
1000	0.17	0.15
1260	0.18	
1600	0.18	
2000	0.19	0.20
2500	0.20	
3160	0.21	
4000	0.22	0.20
5000	0.24	

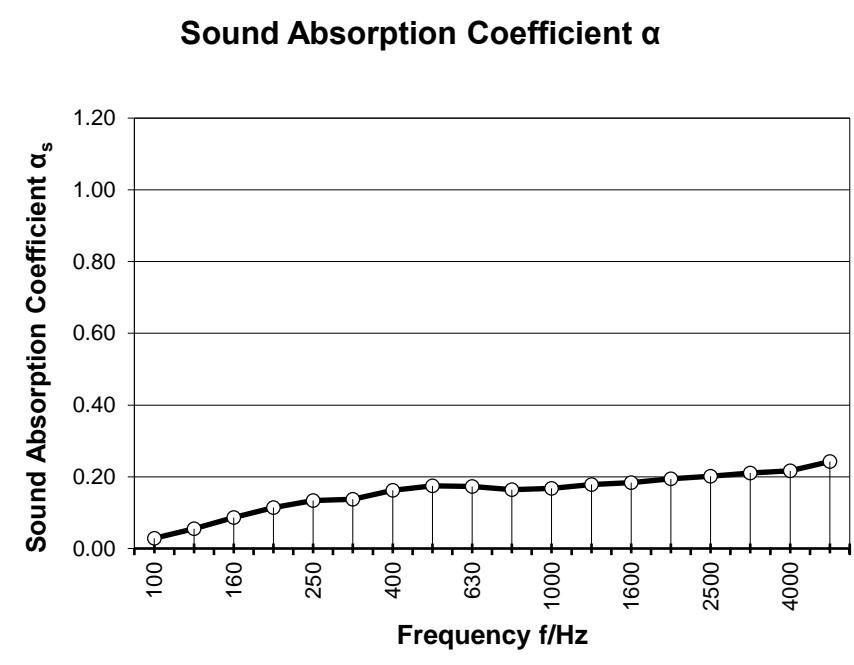

as Sound absorption coefficient to ISO 354

ap Practical sound absorption coefficient to ISO 11654

Rating according to ISO 11654:

NRC:	0.15
SAA:	0.17

Weighted Sound Absorption Coefficient $\alpha_w = 0.2$

Sound absorption class:E

kvadrat soft cells

Test conducted by Kvadrat SoftCells
Poznańska 3, 62-023 Gądk